

织物拉伸测试 Tensile Strength Test Report

客户 Client
行业 Industry Code
测试者 Specialist


Sefar Fabrication (M) Sdn Bhd
/
Mona Chen

测试日期 Date
2011-12-14

- **测试标准 Reference standard:**
ISO 13934-1
GB/T3923.1
- **测试参数设定 Test settings:**
测试宽度 Test width: **50 mm**
测试条样 Test strip dimensions: **50 x 297 mm**
隔距长度 Gauge length: **200 mm**
测试速度 Test speed: **100 mm / min**

滤布型号 Fabric name	TPP-340-236 Overlap Welding	
测试方向 Testing Direction	Warp	
克重 Weight		g/m²
样品来源 Sample source	Provided by Celine Kow	
卷号 Roll No/ ID No	Not mentioned	

测试	断裂强力 (N / 50 mm)	断裂伸长率(%) Elongation	数据分析 Data analysis	分析结果 Results	单位 Unit
测试1 measurement 1	1214.7	15.3	测试样本数 Sample q'ty	3	
测试2 measurement 2	1283.2	15.67	样本均值 Average of Max. breaking force	1209	N/50 mm
测试3 measurement 3	1127.9	13.73	断裂伸长率均值 Average of Elongation at break	14.9	%
测试4 measurement 4			样本标准差 Standard Deviation	78	
测试5 measurement 5			抽样平均误差 Sampling average error	45	
测试6 measurement 6			置信度 Confidence level	0.95	
测试7 measurement 7			自由度 Degree of freedom	2	
测试8 measurement 8			t分布的双侧分位数 Quantile fractile at (t-distribution)	4.30	
测试9 measurement 9			允许误差 Acceptable error	193	
测试10 measurement 10			置信下限 Lower confidence limit	1015	N/50 mm
			置信上限 Upper confidence limit	1402	N/50 mm

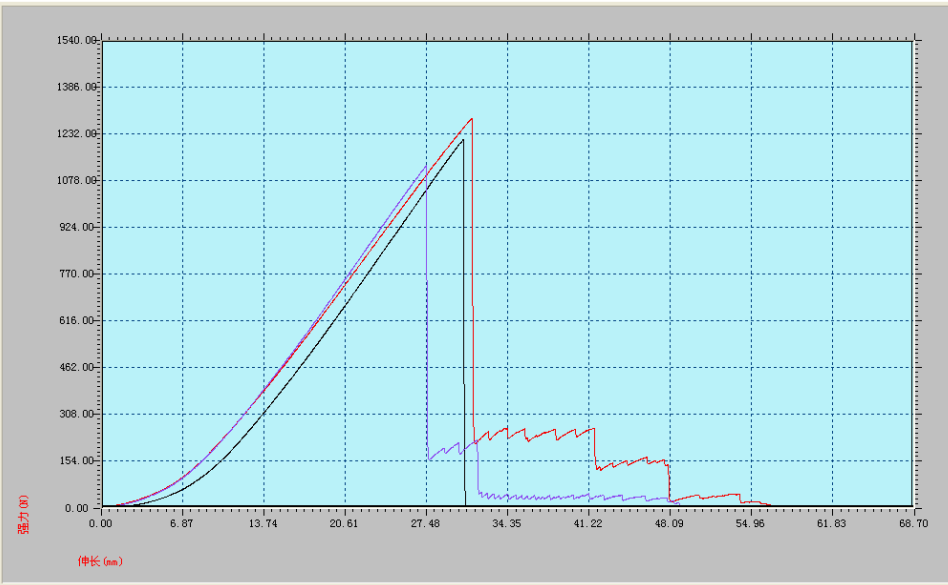

● **结论 Conclusion:**
The test results as above
is only for reference.